

# Experiments and FEM Simulations of Milling Performed to Identify Material Parameters

A. Maurel<sup>1</sup>, M. Fontaine<sup>1</sup>, S. Thibaud<sup>1</sup>, G. Michel<sup>1</sup>, J.C. Gelin<sup>1</sup>

<sup>1</sup>*FEMTO-ST Institute Applied Mechanics department LMARC – 24 chemin de l'épitaphe, 25000 Besançon, France*

*URL: [www.femto-st.fr](http://www.femto-st.fr) e-mail: aurelien.maurel@ens2m.fr*

**ABSTRACT:** An inverse method of identification for the determination of material parameters that are used for the FEM simulation of milling processes is proposed. First of all, a special device has been instrumented and calibrated to perform force and torque measures, directly during milling experiments in using a piezoelectric dynamometer and a high frequency charge amplifier. The experimental results were saved and low pass filtered to obtain a data measured basis reliable and accurate. Then FEM simulations of milling were performed using explicit ALE based FEM code. The material behaviour is firstly described from a Johnson-Cook constitutive law and different characterization tests have been lead in a wide range of conditions to be used to identify a new behaviour law adapted to the process. A fracture model was also added to consider chip formation and separation. Finally, identification procedures are proposed for the determination of material law parameters. These procedures are based on an objective function to minimize, firstly defined by the experimental and numerical results obtained in the turning process and secondly by the experimental and analytical results obtained in milling process. The identification approach is mainly based on the Surfaces Response Method in the material parameters space, coupled to a sensitivity analysis. A Moving Least Square Approximation method is used to accelerate the identification process. This method of identification is here applied for a 304L stainless steel and the first investigations are presented.

**Key words:** FEM, Orthogonal cutting, Milling, 304L Material, Identification, Cutting forces measurements.

## 1 INTRODUCTION

Machining techniques and materials used in aeronautic, automotive or mechanical engineering industries are in constant evolution. The understanding of the physical phenomena and the identification of material behaviour in machining are the main issue for the modelling and optimisation of industrial processes. Some analytical models were previously proposed by Merchant [1] which was developed by Oxley [2] and Molinari & Dudzinski [3], these last works were adapted to milling [4]. More recently, calibrated FEM models appear and seem to progress in the way of the real machining process simulation, Pantalé [5]. Nevertheless, these models give only a partial interpretation of the process's phenomena. To improve predictive capacity of these models, one needs to characterize the material behaviour which is involved in the machining process. Therefore it is emphasized in the present paper to proceed by an inverse method [6] [7] [8] based on FEM or analytical models for the identification of material parameters from machining

experiments.

## 2 NUMERICAL SIMULATION OF MACHINING

### 2.1 Numerical simulation of turning

In order to perform numerical simulation of machining, a finite element model was implemented in LS-Dyna<sup>®</sup> FEM code. As machining is an high speed metal forming process characterized by large dynamic stresses and localized high strains, an explicit code solution scheme was adopted. LS-Dyna<sup>®</sup> FEM code has been chosen to build a Design of Experiment (DOE) empirical model of machining process in order to be able to identify and to understand process parameters. The final aim consists in obtaining a reliable simulation of milling that is one of the more complex cutting processes. At the beginning, orthogonal cutting process has been studied to compare results with bibliography data. In a first stage, a 2D orthogonal cutting model has been developed with LS-Dyna<sup>®</sup> FEM code. Secondly, with these first results in 2D, a 3D oblique cutting model has been developed to improve the

simulation and to correspond to results obtained by Pantalé [5]. The figure 1 relates the distribution of von Mises effective stress contours from simulation results. All this data in orthogonal cutting conditions has shown that LS-Dyna<sup>®</sup> is well adapted to create complex FEM numerical model as milling process.

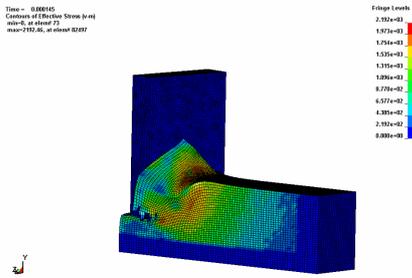


Fig. 1. Von Mises stress contours arising through FEM simulation of orthogonal cutting.

## 2.2 Numerical simulation of milling

Accordingly with the experiments presented in the following part, a 6 mm diameter end mill and a 304L stainless steel rectangular specimen have been designed with SolidWorks<sup>®</sup>, and furthermore industrial cutting conditions have been used in the numerical FEM model.

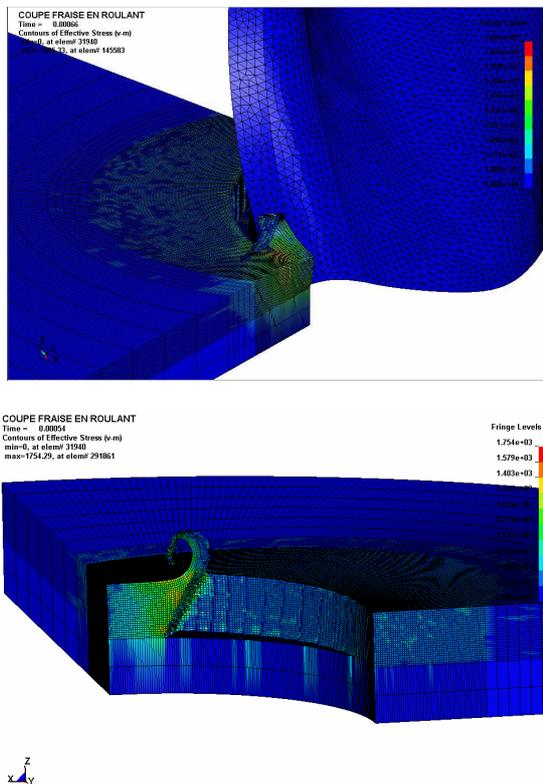


Fig. 2. Von Mises stress contours obtained through simulation results of a milling process numerical model with LS-Dyna software. The cutting conditions are  $N = 20000$  rpm;  $f_t = 0,3\text{mm/tooth}$ ;  $V_c = 250\text{m/min}$ .

Figure 2 relates the first simulation results. The test specimen is meshed with 260,000 elements. The corresponding material behaviour has been firstly modelled using the classical Johnson and Cook constitutive model (1) [9] the parameters of which are provided by the CETIM foundation.

$$\sigma = \left[ A + B(\varepsilon^p)^n \right] \left[ 1 + C \ln \left( \frac{\dot{\varepsilon}^p}{\dot{\varepsilon}_0} \right) \right] \left[ 1 - \left( \frac{T - T_f}{T_{seuil} - T_f} \right)^m \right] \quad (1)$$

The end mill is meshed with about 100,000 elements and considered as a rigid body. This model uses an element failure criterion based on a limiting plastic strain critical value. The calculation time is about 10 days on a bi-processor Xeon 3.21GHz.

## 3 EXPERIMENTAL INVESTIGATIONS

### 3.1 Cutting forces measures during milling

In the first step, a complete instrumentation including sensors and on line measuring system has been set up to obtain repetitive and reliable data. The sensor system is based on a Kistler<sup>®</sup> dynamometer using the piezoelectric accelerometers technology, in order to give, through direct measurement, the cutting forces during the machining process. The experiments were carried out on a KERN<sup>®</sup> micro milling machine as shown in Figure 3. The dynamometer was fixed on the table of the 3 axes CNC machine, and then it was linked to the charge amplifier which was connected to a PC through an input/output acquisition card. The equipments chosen for these milling experiments are as following.



Fig. 3. Experimental data acquisition system used in milling

The types of the selected milling tools are two or four teeth end mills. These tools are uncoated tungsten carbide mills with  $30^\circ$  nominal helix angle and  $12^\circ$  normal rake angle, and the tested diameters are in the range 2-6 mm. All the test specimens have been machined in the same 304L austenitic stainless steel bar and in the same dimensions: 80 mm x 40

mm x 10 mm. All milling experiments have been carried out with a micro lubrication sprayed on the tooling area. The cutting velocities are defined between 50 and 400 m/min to reach a maximum spindle speeds corresponding to 40 000 rpm.

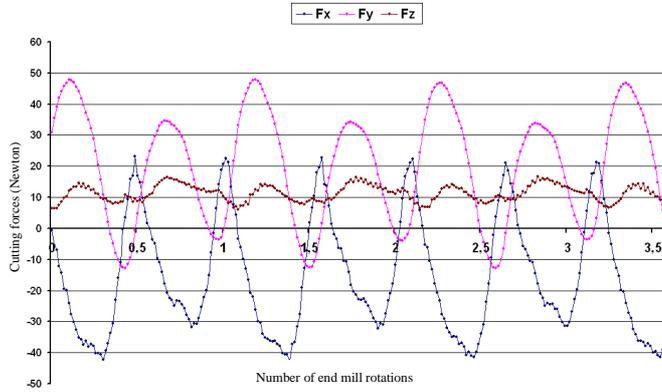


Fig. 4. Cutting forces  $F_x$ ,  $F_y$ ,  $F_z$  vs. end mill rotations.

Figure 4 shows a zoom of the cutting forces stabilized signal in milling where the cutting conditions and machining parameters correspond to:

- 2 teeth end mill  $\varnothing$  4 mm in slotting tests (full radial immersion);
- Spindle speed:  $\Omega = 15920$  rpm; Feed:  $f_t = 0.01$  mm/tooth; Cutting speed:  $V_c = 200$  m/min; Axial depth of cut:  $d_a = 0.5$  mm.

Figure 4 shows that it is possible to get a good and accurate variation of the milling forces on the 3 machine axes. A signal spectral analysis was conducted on forces components in order to check the stability of measured data and to recover the equivalent forces for a rigid case after appropriate low filtering. These accurate and reliable measures allow the understanding of a part of the end mill behaviour during the milling process and then the setting up of the identification process.

#### 4 304L STAINLESS STEEL BEHAVIOUR LAW

In the same time, tensile tests have been performed in the laboratory on the 304L stainless steel provided by the CETIM Research Center. These first experiments allowed us to identify the material parameters of the Johnson-Cook constitutive law (1). This model is based on tensile tests with low speed strain rate. The material parameters are identified by a genetic algorithm applied to the experimental results. Then, to improve this identified model, new tests in partnership with other laboratories of the PGV national project will be realised with high

speed strain rate and a wide range of temperature. O. Lurdos in Saint Etienne has realised high speed strain rate torsion tests, and X. Soldani in Metz has realised double shearing tests and Hopkinson bar tests. A generalised Voce type constitutive law has been identified by O. Lurdos and we will propose a new model adapted to the high speed strain to reach milling cutting conditions. This model will be based on the project rheological tests and identified with numerical simulations of these tests.

The final aim of this work consists in proposing a new constitutive law adapted to the machining process which will be tested in the numerical simulation of milling. The numerical results will be confront to the experimental measures in milling or turning, and a comparison will be tried between the rheological law and the analytical or numerical identified laws.

#### 5 INVERSE IDENTIFICATION METHOD

The final aim of this work consists to lead an inverse identification procedure for the determination of 304L stainless steel parameters of the behaviour law. The identification procedure methodology needs an objective function to minimize, a set of parameters to analyze, a finite element method or analytical solver and a procedure for updating the material parameters. In front of the too big calculation time of the milling simulation, the numerical methodology will be test on the oblique cutting simulation and on cutting forces measures in turning, to prove the feasibility of the method on milling process.

$$R(\mathbf{p}) = \sum_{\text{efforts-mesurés-}n} \frac{1}{2} \left( \sum_{i=1}^{N_p} [F_n^{\text{exp}} - F_n^{\text{num}}(\mathbf{p})]^2 \right) \quad (2)$$

For the milling experiments identification, the parameters system  $\mathbf{p}$  ( $A$ ,  $B$ ,  $n$ ,  $C$ ,  $T_{\text{seuil}}$ ,  $m$ ) has been chosen in the Johnson-Cook constitutive law (1). Then an objective function dependent of the measured experimental criteria (cutting forces) has been defined in (2). The previous function measures difference between the cutting forces curves obtained with the numerical or analytical simulation software and with the experimental device. Figure 5 schematically describes the identification loop, the procedure is based on a set of parameters obtained through simulation and then compared with experimental results. After this estimate, whether the objective function is equal to zero and the optimized

solution appeared, or the function is different to zero and the set of parameters has to be modified and the loop begins one more time. Several methods exist for the modification method. In this work the

Moving Least Square Approximation (MLSA) method has been used.

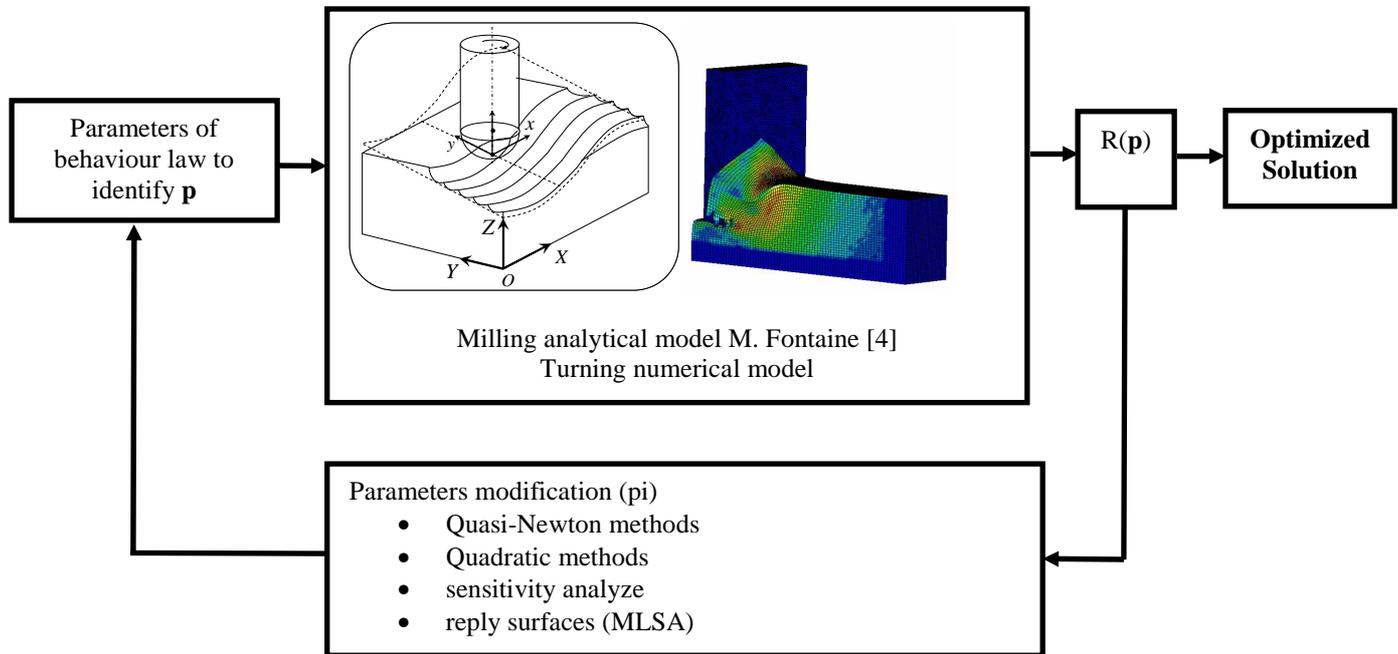


Fig. 5. Diagram representing the inverse identification procedures.

## 6 CONCLUSIONS

Milling experiments allowed us to analyse accurately the measured cutting forces curves and to obtain reliable and useful measured data for the identification procedure. Then, a first 3D simulation of milling process has been set up in industrial conditions. The numerical model is based on a dynamic transient explicit scheme and on Lagrangian formulation. The numerical cutting forces obtained give good results in matter of forces values and curves shapes. But we will set up soon simulation with industrial tools to compare numerical and experimental results. At the end, this paper described the identification procedure which will be set up on analytical milling or numerical turning models. Moreover, further developments are in progress and concern the numerical model improvements, the identification of a new material behaviour model and the set up of characterisation turning tests with the same material.

## ACKNOWLEDGEMENTS

This work has been carried out with the financial support from the CETIM Foundation in the frame of PGV1 national project.

## REFERENCES

1. E. Merchant, Basic mechanics of the metal cutting process, *J. of Applied Mechanics*, 66, (1944) 168-175.
2. P.L.B. Oxley, *Mechanics of metal cutting*, ASME, (1963) 50-60.
3. A. Molinari, D. Dudzinski, Stationary shear band in high speed machining, *C.R. Acad. Sciences Paris*, 315 (II), (1992) 399-405.
4. M. Fontaine, A. Devillez, A. Moufki and D. Dudzinski, Predictive force model for ball end milling and experimental validation with a wavelike form machining test, *Int. J. Machine Tools and Manufacture*, 46, (2006) 367-380.
5. O. Pantalé, "Modelling and three-dimensional simulation of metal cutting", Ph.D. Thesis, Bordeaux I University, 1996.
6. J.C. Gelin, C. Labergere, Application of optimal design and control strategies to the hydroforming of thin walled metallic tubes, *Int. J. Forming Processes*, 7, (2004) 141-158.
7. O. Ghouati, J.C. Gelin, Identification of material parameters directly from metal forming processes, *J. Material Processing Technology*, 80-81, (1998) 560-564.
8. O. Ghouati, J.C. Gelin, A finite element based identification method for complex material behaviours, *Computational Materials Science*, 21, (2001) 57-68.
9. G.R. Johnson, W.H. Cook, Constitutive model and data for metals subjected to large strains, high strain rates, and high temperatures, *Proc. 7th Symp. On Ballistics*, Netherlands(1983).